EE 232 Lightwave Devices
Lecture 3: Basic Semiconductor Physics and Optical Processes

Instructor: Ming C. Wu

University of California, Berkeley
Electrical Engineering and Computer Sciences Dept.

Optical Properties of Semiconductors
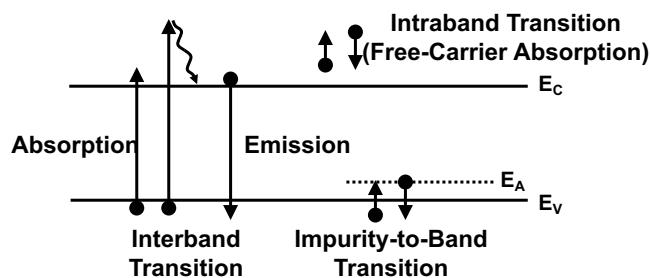
- **Optical transitions**
  - **Absorption: exciting an electron to a higher energy level by absorbing a photon**
  - **Emission: electron relaxing to a lower energy state by emitting a photon**

Band-to-Band Transition

- **Since most electrons and holes are near the band-edges, the photon energy of band-to-band (or interband) transition is approximately equal to the bandgap energy:**

$$hv = E_g$$

- **The optical wavelength of band-to-band transition can be approximated by**

$$\lambda = \frac{c}{v} = \frac{hc}{E_g} \approx \frac{1.24}{E_g}$$

λ : wavelength in μm

E_g : energy bandgap in eV

Energy Band Diagram in Real Space and k-Space
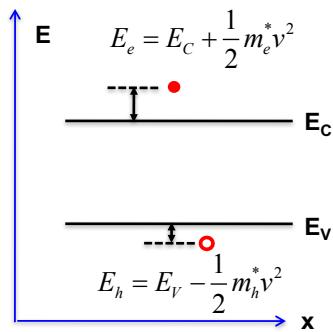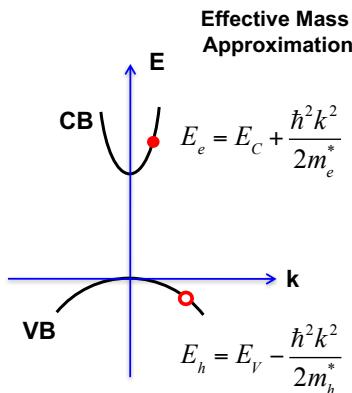
Effective Mass Approximation

$$E_e = E_C + \frac{1}{2} m_e^* v^2$$

E

E_C

E_V

$$E_h = E_V - \frac{1}{2} m_h^* v^2$$

x

Momentum:
$$\hbar k = m_e^* v_e$$

E

CB

$$E_e = E_C + \frac{\hbar^2 k^2}{2m_e^*}$$

k

VB

$$E_h = E_V - \frac{\hbar^2 k^2}{2m_h^*}$$

Real Space

K-Space

Band-to-Band Transition

CB

hν

VB

Absorption

⬇

Photodetectors; Solar Cells

CB

hν

VB

Spontaneous Emission

⬇

LED

CB

hν   **hν**

VB

Stimulated Emission

⬇

Optical Amplifiers; Semiconductor Lasers
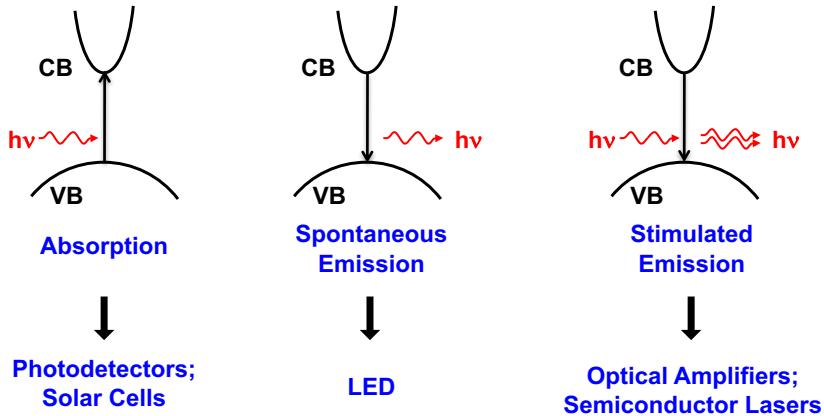
Prof. Ming Wu

Conservation of Energy and Momentum

CB

E₂

hν

VB

E₁

E

k

k₁ **k₂**
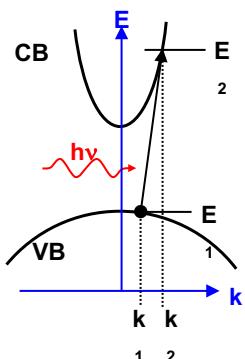
Optical transitions are "vertical" lines

- **Conditions for optical absorption and emission:**
  - **Conservation of energy**

  $$E_2 - E_1 = h\nu$$

  - **Conservation of momentum**

  $$k_2 - k_1 = k_{h\nu}$$

  $$k_2, k_1 \sim \frac{2\pi}{a}$$

  $$k_{h\nu} \sim \frac{2\pi}{\lambda}$$

  $$\left(a \sim 0.5nm \right) << \left(\lambda \sim 1\mu m \right)$$

  Lattice Constant

  $$\Rightarrow k_2 = k_1$$

Prof. Ming Wu

Direct vs Indirect Bandgaps

CB

VB

hν

CB

VB

Phonon

hν

X
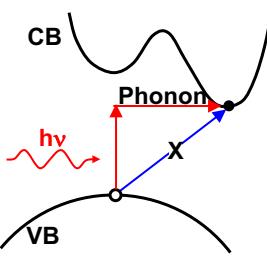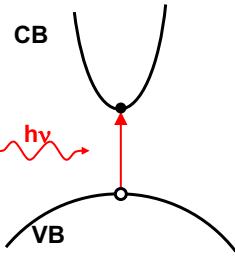
- **Direct bandgap materials**
  - **CB minimum and VB maximum occur at the same k**
  - **Examples**
    - **GaAs, InP, InGaAsP**
    - **(Al$_x$Ga$_{1-x}$)As, x < 0.45**

- **Indirect bandgap materials**
  - **CB minimum and VB maximum occur at different k**
  - **Example**
    - **Si, Ge**
    - **(Al$_x$Ga$_{1-x}$)As, x > 0.45**
  - **Not "optically active"**

Absorption Coefficient

$h\nu$ (eV)

300K

Ge($\lambda_c = 1.24/E_g = 1.88$ μm)

Ga$_{.30}$In$_{.70}$As$_{.64}$P$_{.36}$
(1.4 μm)

GaAs
(0.87 μm)

CdS
(0.51 μm)

Si (1.1 μm)

a −Si
(0.82 μm)

Absorption coefficient α (cm^{-1})

Light penetration depth 1/α (μm)

Wavelength (μm)
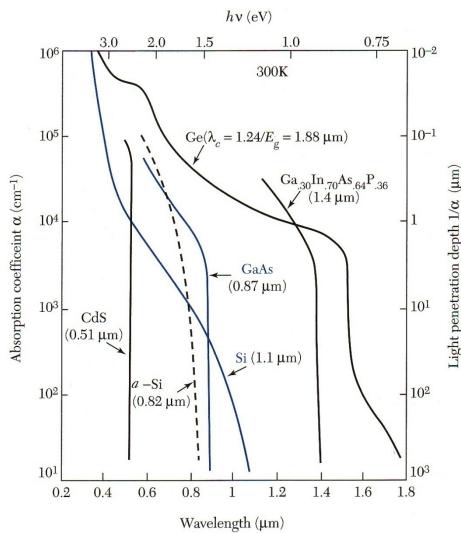
- **Light intensity decays exponentially in semiconductor:**

$$I(x) = I_0 e^{-\alpha x}$$

- **Direct bandgap semiconductor has a sharp absorption edge**

- **Si absorbs photons with hν > E$_g$ = 1.1 eV, but the absorption coefficient is small**
  - **Sufficient for CCD**

- **At higher energy (~ 3 eV), absorption coefficient of Si becomes large again, due to direct bandgap transition to higher CB**

Review of Semiconductor Physics
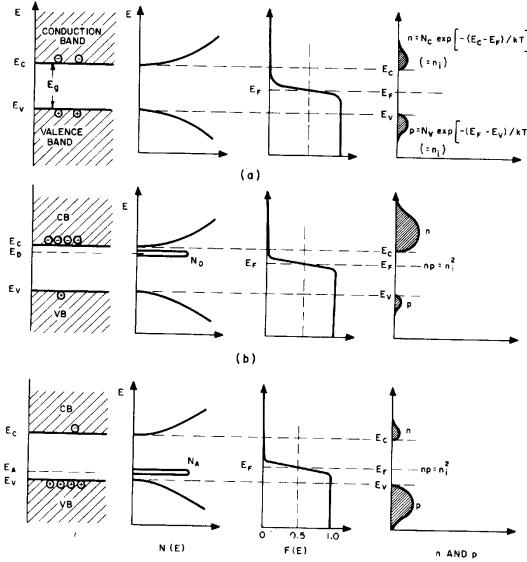
Electron and hole concentrations:

$$n = \int_{E_C}^{\infty} f_n(E)\rho_e(E)dE$$

$$p = \int_{-\infty}^{E_V} f_p(E)\rho_h(E)dE$$

Fermi-Dirac distributions:

$$f_n(E) = \frac{1}{1 + \exp\left(\dfrac{E - F_n}{k_B T}\right)}$$

$$f_p(E) = \frac{1}{1 + \exp\left(\dfrac{F_p - E}{k_B T}\right)}$$

F_n : electron quasi-Fermi level

F_p : hole quasi-Fermi level

EE232 Lecture 3-9　　　　　　　　　　　　　　　　　　　Prof. Ming Wu

Electron/Hole Density of States (1)
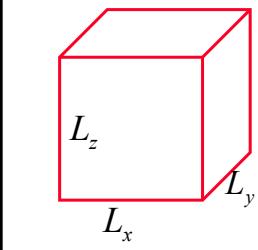
- **Electron wave with wavevector k**

$$e^{i\vec{k}\cdot\vec{r}}$$

- **Periodic boundary conditions**

$$e^{i\vec{k}\cdot\vec{r}} = e^{i\vec{k}\cdot\left(\vec{r}+L_x\vec{x}\right)} = e^{i\vec{k}\cdot\left(\vec{r}+L_y\vec{y}\right)} = e^{i\vec{k}\cdot\left(\vec{r}+L_z\vec{z}\right)}$$

- **An electron state is defined by**

$$\left(k_x, k_y, k_z\right)\uparrow\downarrow = \left(m\frac{2\pi}{L_x}, n\frac{2\pi}{L_y}, l\frac{2\pi}{L_z}\right)\uparrow\downarrow$$
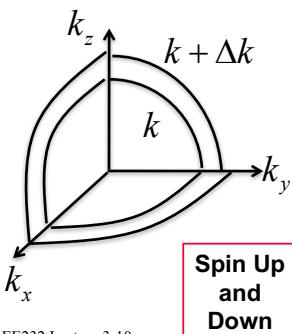
- **Number of electron states between k and k + Δk in k-space per unit volume**

Spin Up and Down

$$\frac{2}{V} \cdot \frac{4\pi k^2 dk}{\dfrac{2\pi}{L_x}\dfrac{2\pi}{L_y}\dfrac{2\pi}{L_z}} = \frac{k^2}{\pi^2} dk = \rho_k(k)dk$$

EE232 Lecture 3-10　　　　　　　　　　　　　　　　　　Prof. Ming Wu

Electron/Hole Density of States (2)

- **Number of electron states between E and E + ΔE per unit volume**

$$E = E_C + \frac{\hbar^2 k^2}{2m_e^*} \Rightarrow dE = \frac{\hbar^2 k}{m_e^*} dk$$

$$\frac{k^2}{\pi^2} dk = \frac{m_e^*}{\hbar^2 \pi^2} \frac{\sqrt{2m_e^*\left(E - E_C\right)}}{\hbar} dE = \rho_e(E) dE$$

$$\rho_e(E) = \frac{1}{2\pi^2}\left(\frac{2m_e^*}{\hbar^2}\right)^{3/2} \sqrt{E - E_C}$$

- **Likewise, hole density of states**

$$\rho_h(E) = \frac{1}{2\pi^2}\left(\frac{2m_h^*}{\hbar^2}\right)^{3/2} \sqrt{E_V - E}$$

Prof. Ming Wu

Electron and Hole Concentrations

$$n = \int_{E_C}^{\infty} f_n(E)\rho_e(E)\,dE = \int_{E_C}^{\infty} \frac{1}{1+\exp\left(\dfrac{E - F_n}{k_B T}\right)} \frac{1}{2\pi^2}\left(\frac{2m_e^*}{\hbar^2}\right)^2 \sqrt{E - E_C}\,dE$$

$$\boxed{n = N_C \cdot F_{1/2}\left(\frac{F_n - E_C}{k_B T}\right)}$$

$$N_C = 2\left(\frac{\pi m_e^* k_B T}{2\pi^2 \hbar^2}\right)^{3/2}$$

Fermi-Dirac Integral

$$F_j(\eta) = \frac{1}{\Gamma(j+1)} \int_0^{\infty} \frac{x^j}{1+e^{x-\eta}} dx$$

$$\boxed{\text{p=}N_V \cdot F_{1/2}\left(\frac{E_V - F_p}{k_B T}\right)}$$

Gamma Function

$$\Gamma\left(\frac{3}{2}\right) = \frac{\sqrt{\pi}}{2}$$

$$N_V = 2\left(\frac{\pi m_h^* k_B T}{2\pi^2 \hbar^2}\right)^{3/2}$$

Prof. Ming Wu

Approximation of Electron/Hole Concentration

$$F_j(\eta) = \frac{1}{\Gamma(j+1)} \int_0^\infty \frac{x^j}{1+e^{x-\eta}} dx \approx \begin{cases} e^\eta & \text{when } \eta \ll 1 \\ \frac{4}{3}\left(\frac{\eta^3}{\pi}\right)^{1/2} & \text{when } \eta \gg 1 \end{cases}$$

When $F_n \ll E_C$ (Boltzmann approximati...

$$n \approx N_C \cdot e^{-\frac{E_C - F_n}{k_B T}}$$

When $F_n \gg E_C$ (Degenerate)

$$n \approx N_C \cdot \frac{4\left(\frac{F_n - E_C}{k_B T}\right)^{3/2}}{3\sqrt{\pi}}$$

$\dfrac{n}{N_C}$

Boltzmann Approx

Degenerate

Quasi-Fermi Level Cross Band Edge

$\dfrac{F_n - E_C}{k_B T}$

Prof. Ming Wu